

PRO-SET®

Technical Data

LAM-145

LAM-237

LAMINATING EPOXY

The New
Standard

EPOXIES for
Laminating
Infusion
Tooling
Assembly

Wessex Resins & Adhesives

Cupernham House
Cupernham Lane
Romsey, Hampshire
SO51 7LF, UK
pro-set.co.uk
+44(0)1794 521111

ISO9001:2015 Certified

REV 4 / Apr 2018

©2018 Wessex Resins
& Adhesives

COMBINED FEATURES

Medium viscosity for good wet out of all synthetic composite fabrics and core materials.

Thixotroped to prevent drain out in heavy fabrics and on vertical surfaces.

High tack to help hold heavy fabric and core in place on vertical surfaces.

Extra slow cure speed hardener provides 7 to 8 hours of working time at 25°C. A typical laminate will be gelled in 12 to 14 hours.

Optimized for hand wet out and machine impregnation in contact moulding, vacuum bagging and filament winding applications.

Room temperature cure properties suitable for many composite components and structures.

Tg as high as 101°C with proper post cure providing excellent temperature stability and great part cosmetics.

Cost effective, high performance epoxy formulation for synthetic composite manufacturing.

HANDLING PROPERTIES

Property	Standard	Units	22°C	25°C	29°C
150g Pot Life	ASTM D2471	minutes	197	128	100
500g Pot Life	ASTM D2471	minutes	135	107	75
Viscosity Mixed	ASTM D2196	mPas	1700	1495	1152
Viscosity (resin)	ASTM D2196	mPas	10,000		
Viscosity (hardener)	ASTM D2196	mPas	27		
Shear Thinning Index	ASTM D2196	-	1.45		


MIX RATIO

Method	Resin:Hardener	Resin:Hardener
Weight	3.5:1	100:28.6
Volume	3.00:1	100:33.3

DENSITY

State	Units	21°C
Cured	gcm ⁻³	1.16
Resin	gcm ⁻³	1.17
Hardener	gcm ⁻³	0.97

VISCOSITY VS TEMPERATURE

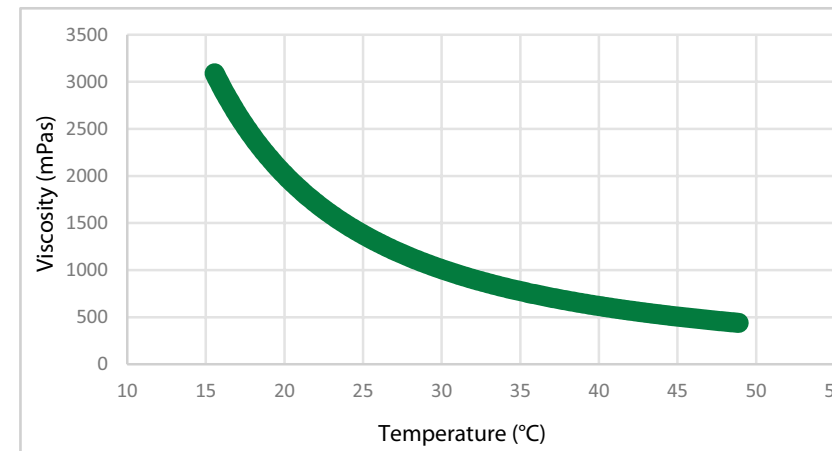

Test specimens were neat epoxy (without fibre reinforcement).
Typical values not to be construed as specification.

LAM-145 / LAM-237

LAMINATING EPOXY

MECHANICAL PROPERTIES

Property	Standard	Units	22°C x 4 Weeks	25°C x 2 Weeks	RT Gelation + 49°C x 8 hrs	RT Gelation + 60°C x 8 hrs	RT Gelation + 82°C x 8 hrs
Hardness	ASTM D2240	Shore D	84	85	86	86	86
Compression Yield	ASTM D695	MPa	106	107	99	99	99
Tensile Strength	ASTM D638	MPa	62	58	67	70	72
Tensile Modulus	ASTM D638	GPa	3.82	3.79	3.49	3.45	2.91
Tensile Elongation	ASTM D638	%	1.9	1.9	3.2	3.9	6.7
Flexural Strength	ASTM D790	MPa	96	106	118	120	127
Flexural Modulus	ASTM D790	GPa	3.77	3.44	3.44	3.41	2.79

THERMAL PROPERTIES

Property	Standard	Units	22°C x 4 Weeks	25°C x 2 Weeks	RT Gelation + 49°C x 8 hrs	RT Gelation + 60°C x 8 hrs	RT Gelation + 82°C x 8 hrs	
Tg DMA Peak Tan Delta	ASTM E1640*1	°C	69	69	86	93	111	
Tg DMA Onset Storage Modulus	ASTM E1640*1	°C	62	62	74	80	101	
Tg DSC Onset - 1st Heat	ASTM E1356	°C	57	58	65	75	88	
Heat Deflection Temperature	ASTM D648	°C	56	56	64	72	82	
Tg DSC Ultimate	ASTM E1356	°C	102*2					

*1 1Hz, 3°C per minute.

*2 Additional post cure may be required; contact Technical Department for details.

Test specimens were neat epoxy (without fibre reinforcement).

These are typical properties and cannot be construed as a specification. The end users should test the products to ensure the products are suitable for the intended application. Any information, data, advice or recommendation published by Wessex Resins or obtained from Wessex Resins by other means and whether relating to Wessex Resins' materials or other materials, is given in good faith and believed to be reliable.

REV 4 / Apr 2018